



Micro-8

RoHS Compliance Document

Contents:

1. Composition
2. Solder Reflow
3. Tin Whisker Report



International Rectifier


41915 Business Park Drive, Temecula, California 92590 * Telephone (951) 676-7500



MICRO-8

Component	Material Name	Material Mass (g)	Element Name Composition	CAS #	Substance Mass (g)	Material Analysis Weight (%)	% of Total Weight
Chip	Silicon	0.00069	Si	7440-21-3	0.00069	100%	2.7%
Encapsulant	Epoxy Resin	0.01465	SiO2	7631-86-9	0.01055	72%	41.3%
			Epoxy	90598-46-2	0.00366	25%	14.3%
			Other	-	0.00044	3%	1.7%
Lead Frame	Copper	0.00899	Cu	7440-50-8	0.00877	98%	34.3%
			Fe	7439-89-6	0.00022	2%	0.9%
Die Attach	Silver Epoxy	0.00018	Ag	7440-22-4	0.00015	84%	0.6%
			Epoxy	90598-46-2	0.00003	16%	0.1%
Wire bond	Gold	0.00021	Au	7440-57-7	0.00021	100%	0.8%
Lead Finish	Matte Tin	0.00082	Sn	7440-31-5	0.00082	100%	3.2%
Total Weight (g)					0.02554		

* Tin whisker mitigation strategy is 150 C, 1 hour anneal within 24 hours of tin plating.

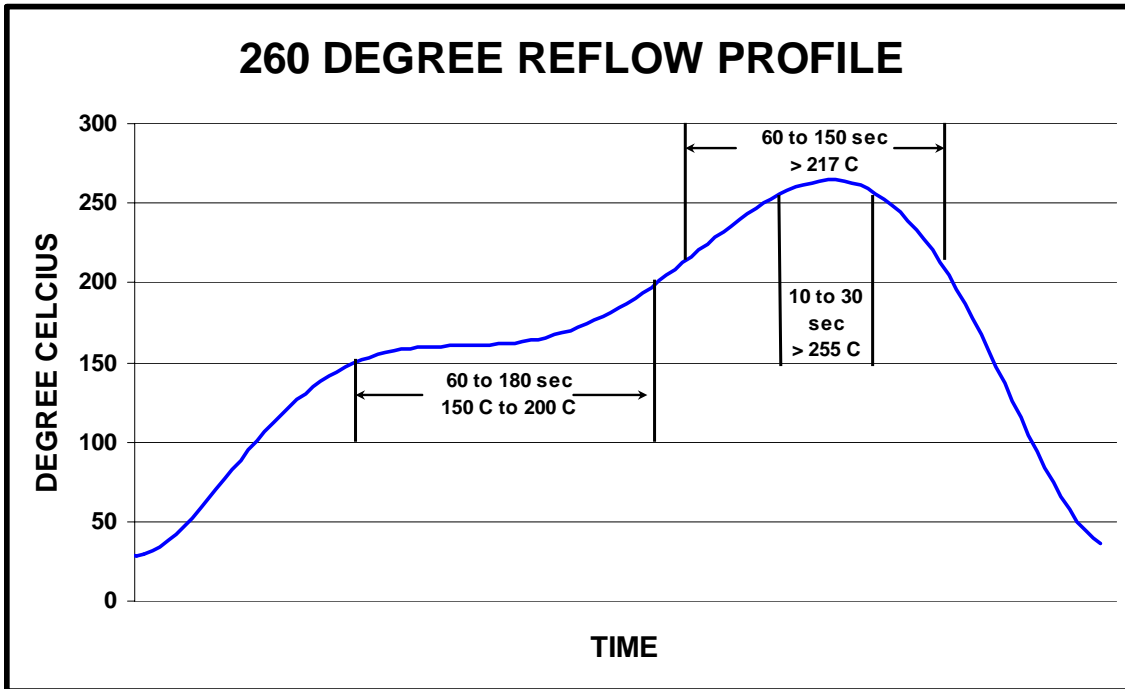

This part is compliant with EU Directive 2002/95/EC (RoHS) and does not contain lead, mercury, cadmium (0.01%), hexavalent chromium, PBB or PBDE in concentrations greater than 0.1%, except as permitted by Annex (7).

The information contained in this document is provided without any warranty, either expressed or implied, and IR specifically disclaims any and all liability, including but not limited to consequential or indirect damages.



MICRO-8

Test Definition	Test Conditions	Inspection Interval Class 1 and 2 Products	Total Duration Class 1 and 2 Products	Maximum Whisker Length (um)
Room Temperature Humidity Storage	30± 2°C/60± 3% RH	1000 hours	4000 hours	20
Temperature Humidity Unbiased	55± 3°C/85±3% RH	1000 hours	4000 hours	20
Temperature Cycling	-40 to 55°C to 80 to 95°C, air to air, 10 min soak, approx 3 cycles /hours	500 cycles	1500 cycles	45

Tin Whisker testing per JESD201, Environmental Acceptance Requirements for Tin Whisker Susceptibility of Tin and Tin Alloy Surface Finish

Tin Whisker Results (number of failing whiskers)

Test	1000 Hours	2000 Hours	3000 Hours	4000 Hours
Room Temperature Humidity Storage	0/24	0/24	0/24	0/24
Temperature Humidity Unbiased	0/24	0/24	0/24	0/24
Test	500 Cycles	1000 Cycles	1500 Cycles	
Temperature Cycling	0/24	0/24	0/24	